

TEST RESULTS (Cont.)

CAN/ULC-S109-03 Large Flame Test

Standard Methods of Tests for Flame-Resistant Textiles and Films


Tested "as received" and in single sheet configuration.

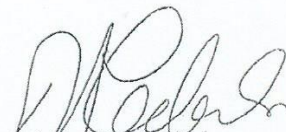
		Damaged Length (mm)	Flaming Dripping (s)	Afterflame Time (s)	
Direction 1	1:	150	0.0	12.3	
	2:	129	0.0	0.0	
	3:	131	0.0	0.0	
	4:	120	0.0	0.0	
	5:	91	0.0	0.0	
Direction 2	6:	115	0.0	0.0	
	7:	152	0.0	0.0	
	8:	95	0.0	0.0	
	9:	125	0.0	0.0	
	10:	139	0.0	0.0	
Average:		125	-	-	
Maxima Specified by ULC-S109 Large Flame Test:		250	-	-	(average)
		-	2.0	-	(individual)

(Above tip of test flame)

CONCLUSIONS

When tested "as received", the material identified in this report meets the flame resistance requirements of both the Small-Flame and Large-Flame Tests of CAN/ULC-S109-03.


 Lucilia Godinho,
 Fire Testing


 Richard J. Lederle,
 Fire Testing

Note: This report consists of 3 pages, including the cover page, that comprise the report "body". It should be considered incomplete if all pages are not present. Additionally, the Appendix of this report comprises a cover page, plus 1 page.